

www.assuredtesting.com  
388 Servidea Drive  
Ridgway, PA 15853 USA  
P: +1 814-773-3224  
F: +1 814-773-3225

**Customer:** Basecrete Technologies  
**Purchase Order#** 855493  
**Quote #:** 042922BCT  
**Primary Contact:** Loyal Dodd

**BILL TO:** FLSARASOT--3757  
Basecrete Technologies  
8255 Consumer Ct, Lot 25  
Sarasota FL 34240  
USA  
Ph: 941-312-5142

**SENT TO:** FLSARASOT--3757  
Basecrete Technologies  
8255 Consumer Ct, Lot 25  
Sarasota FL 34240  
USA  
Ph: 941-312-5142

# TEST REPORT - 33215

Entry Date: Monday, May 9, 2022

Pull Off Adhesion IAW ASTM D4541, Method E, Type V.

See attached photos.

## Part and Test Information

Test Result	Test Name/Procedure	Adhesion ASTM D4541-17 Method E Pull-off Strength
Results: See below.	Requirement Specification	Unspecified
Sample 1 (White layer: PANELTIM MP2DS Panel / Green/Grey layer: BASECRETE flexible waterproof bondcoat): 1) 214 psi - 100% cohesive removal 2) 180 psi - 100% cohesive removal	Customer Material Specification	
Sample 2 (White layer: PANELTIM 1DS Panel / Green/Grey layer: BASECRETE flexible waterproof bondcoat): 1) 113 psi - 15% total removal with 85% cohesive removal 2) 88 psi - 30% total removal with 70% cohesive removal	Part Number	
Sample 3 (Black layer: PANELTIM AS5R Panel / Green/Grey layer: BASECRETE flexible waterproof bondcoat): 1) 131 psi - 100% cohesive removal 2) 101 psi - 25% total removal with 75% cohesive removal	Lot Number	
Customer Requested Parameters: 20mm dollies, 2 pulls per sample with scoring.	Sample Description	17" x 12" x 2" Coated Plastic Samples
Requirements: No pass / fail criteria provided. Report results and PSI.	In Date	12-May-22
	Out Date	13-May-22
	Test Count	3
	Return Count	3
	Cycles	Hours
	Required	Required
	Hours/Cycle	Completed
	Completed	

# TEST REPORT - 33215

Assured Testing Services

**BILL TO:** FLSARASOT--3757  
Basecrete Technologies

**SENT TO:** FLSARASOT--3757  
Basecrete Technologies

**Isabella Cadori**  
**Laboratory Analyst**



Issue Date: 5/20/2022

**End Of Report**

Test results apply only to the item(s) as received and as tested. If Assured Testing Services needs to manipulate a test item dimensionally for the purpose of equipment parameters the results only apply to the portion that is tested. When Information supplied by the customer could affect test results, the customer is responsible for the determining validity of the reported results. Information and statements in this report are derived from material, information, and/or specifications furnished by the client and exclude any expressed or implied warranties as to the fitness of material tested or analyzed for any particular purpose or use. This report is confidential property of our client and may not be used for advertising purposes. This report shall not be reproduced except in full, without written approval of this laboratory. This recording of false, fictitious or fraudulent statements or entries on this document may be punished as a felony. Samples will be discarded 2 weeks following issuance of test report, unless notified in writing by the client. Any client claims or damages arising from the use of information in this report are strictly limited to the cost of the services provided by Assured Testing Services.

**Revision: 5/3/2022**

**Assured Testing Services, Ridgway, PA**  
**TR33215** **Basecrete Technologies**  
**Photos of Samples tested for Pull Off Adhesion**  
**IAW ASTM D4541-17 Method E Type V**




Sample 1: Two individual completed tests with corresponding dollies after pull-off adhesion – (See above)



Sample 2: Two individual completed tests with corresponding dollies after pull-off adhesion – (See above)



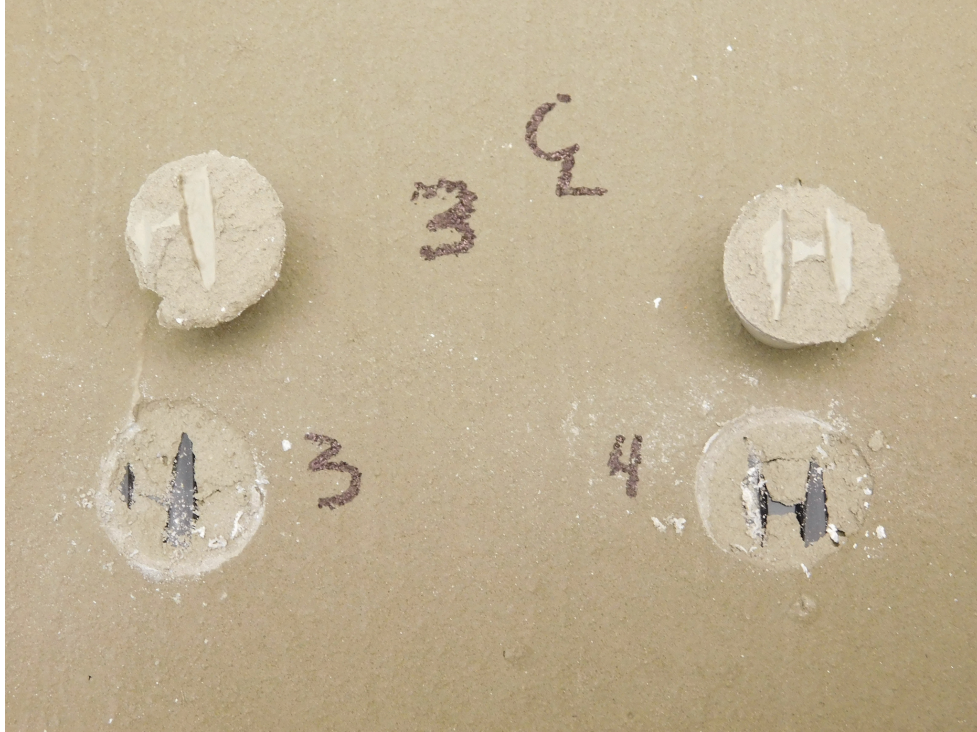

Sample 3: Two individual completed tests with corresponding dollies after pull-off adhesion – (See above)

End of Photo Page